arXiv:1405.7852v1 [cond-mat.mtrl-sci] 30 May 2014

Pressure induced ferroelastic phase transition in $LuLiF_4$ compound

Anastasia Petrova[a], Oleg Nedopekin[a], Dmitrii Tayurskii[a,b], Benoit Minisini[c]

[a] *Institute of Physics, Kazan Federal University, Kremlevskaya St. 16a, 420008 Kazan, Russia*
[b] *Centre for Quantum Technologies, Kazan Federal University, Kremlevskaya St. 16a, 420008 Kazan, Russia*
[c] *Institut Supérieur des Matériaux et Mécaniques Avancés du Mans, 44 Avenue Bartholdi, 72000 Le Mans, France*

Abstract

The behavior of $LuLiF_4$ sheelite ($I4_1/a$, Z = 4) under hydrostatic pressure was investigated by means of the first principles calculations. The ferroelastic phase transition from the tetragonal structure of $LuLiF_4$ to fergusonite structure ($C_{12}/c1$, Z = 4) has been found at 10.5 GPa. It has been determined that this is the second order phase transition.

Keywords: A. Fluorides, D. Pressure induced phase transitions

1. Introduction

The interest to fluorite rare-earth compounds (with the scheelite $CaWO_4$ structure) increases significantly due to their possible application in laser technologies and microelectronics. The intrinsic dipole moment materials invoke the particular curiosity in a certain temperature range. One of these compounds (namely, $LuLiF_4$) has been recently investigated at high pressures by synchrotron angle-dispersive x-ray powder diffraction in a diamond anvil cell at room temperature [1]. A tricritical phase transition to the fergusonite crystal structure was found at 10.7 GPa, but the type of this phase transition remained unknown. The present article is devoted to the searching for the phase transi-

Email address: npetrova131@gmail.com (Anastasia Petrova)

tion in $LuLiF_4$ at high pressures by means of density functional theory (DFT) [2, 3] and to identification of its type.

2. Calculations

Two possible crystal structures of $LuLiF_4$ with symmetries $I4_1/a$ and C12/c1 were investigated by means of ab-initio calculations. VASP 5.2 (Vienna Ab-Initio Simulation Package)[4] software package, the part of MedeA[1] modeling interface, was used to perform the first principles DFT calculations. The geometry of structures was optimized in the range of the pressures from 0 GPa to 20 GPa with 2 GPa step until the maximum force dropped below 0.005 eV/Å, whereas the self-consistent field energy convergence criterion was set at 10^{-6} eV.

All calculations were performed in "non magnetical" mode (i.e. two electrons in each state). The electronic degrees of freedom were described using the projector augmented wave method [5] and basis of plane waves as implemented in VASP 5.2. The valence electrons of Lu were considered as the "kept frozen in the core". The exchange-correlation functional has been approximated by the gradient corrected form proposed by Perdew-Burke-Ernzerhof [6]. The Dudarev approach [7] was applied within simplified generalized gradient approximation (GGA)+U scheme [6]. The other calculation parameters were chosen the same as in the paper [8].

3. Results

The analysis of lattice parameters, unit cell volume, order parameter and bulk modulus under pressure has been performed in order to determine the type of phase transition and to obtain the transition pressure. In FIG. 1 (a) the pressure dependencies of the lattice parameters (where a_m, b_m and c_m are the lattice parameters of monoclinic structure; a_0, b_0, c_0 are respective values of the lattice parameters at ambient pressure) reflecting the transformation of the structure from $I4_1/a$ to the C12/c1 symmetry are shown. Since C12/c1

[1] Materials Design, S.A.R.L.

symmetry group is a subgroup of $I4_1/a$, the structural parameters of these symmetries coincide below 10.5 GPa. Based on these results we can conclude that the phase transition occurs at 10.5 GPa that is in a good agreement with the experimental data [1].

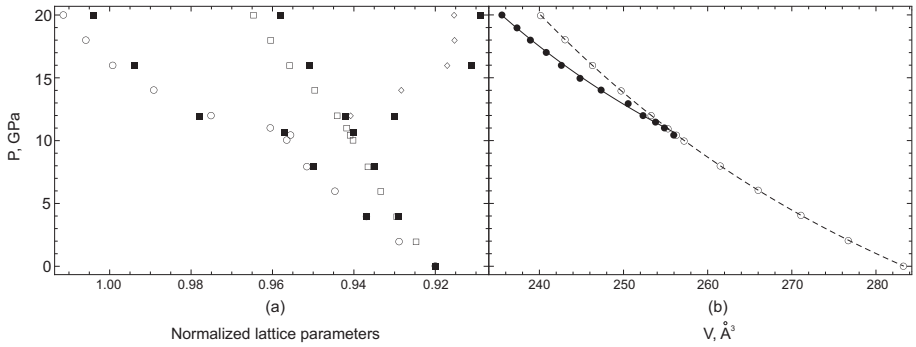

Figure 1: (a) pressure dependencies of the lattice parameters ($LuLiF_4$ structure, C12/C1 symmetry) normalized to the respective value at ambient pressure: experimental values [1]- solid square; ab-initio calculations- empty diamond- a^m/a_0, empty square- b^m/b_0, empty circle- c^m/c_0); (b) the empty circles- the unit-cell volume of $I4_1/a$ $LuLiF_4$ structure versus the pressure, the solid circles- the unit-cell volume of C12/c1 $LuLiF_4$ structure versus the pressure, dashed and solid lines- Birch Murnaghan approximation.

In order to identify the type of phase transition the volumes of $LuLiF_4$ unit cell for two symmetries were calculated for pressure up to 20 GPa. FIG. 1 (b) demonstrates the difference of the cell volumes between two symmetries above 10.5 GPa. It is well known that the energy and the volume of the system are changing smoothly at the second order phase transition [9], which is accompanied by the changes of the system symmetry as in the present case. Based on FIG.1 we can conclude that the second order phase transition occurs in the analyzed compound $LuLiF_4$ at high pressures.

The order parameter versus the pressure was plotted to find critical pressure of the phase transition. The second rank strain tensor components have been selected as a primary order parameter [1]. The tensor function has the following form $\mathbf{e}_m = 1/\sqrt{2}(\mathbf{e}_{xx} - \mathbf{e}_{yy})$ [10]. The spontaneous strains $\mathbf{e}_{xx}$ and $\mathbf{e}_{yy}$, contributing to the order parameter $\mathbf{e}_m$, are determined as follows: $\mathbf{e}_{xx} = (c_m - a_t)/a_t, \mathbf{e}_{yy} = (a_m/\sqrt{2} - a_t)/a_t$ (where a_t is a lattice parameter of tetrag-

onal structure, a_m and c_m are the lattice parameters of monoclinic structure). The order parameter starts to change smoothly from zero ($I4_1/a$ symmetry) to a nonzero (C12/c1 symmetry) value at the point 10.5 GPa (see FIG. 2).

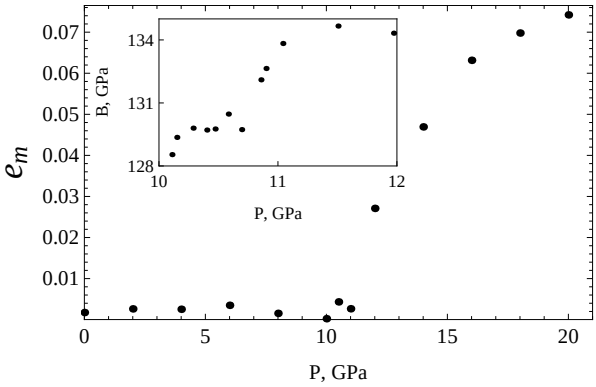

Figure 2: The order parameter of $LuLiF_4$ structure versus the pressure. Inset shows the pressure dependence of the bulk modulus of $LuLiF_4$ structure.

The dependence of bulk modulus B on pressure from 0 GPa to 12 GPa was also investigated. The change in the behavior was observed from 10.5 GPa to 11 GPa on FIG. 2. The bulk modulus $B = 16$ GPa, volume $V = 323.4$ $\mathring{A}^3$, and first pressure derivatives of the bulk modulus $B_0' = 9.9$ for C12/c1 symmetry were calculated by fitting the pressure-volume compression data with Birch - Murnaghan equation of state [11]. The same parameters for $I4_1/a$ symmetry at ambient pressure have been obtained previously [8]. The pressure derivatives of the bulk modulus of two symmetries $LuLiF_4$ structure are extremely different.

Analogous compound $YLiF_4$ was also studied by means of the DFT method in the previous paper [12]. It has been shown that $YLiF_4$ undergoes the phase transitions from the scheelite phase ($I4_1/a$, Z = 4) to the fergusonite-like phase (I_2/a, Z = 4) and to the $LaTaO_4$ like-phase ($P2_1/c$, Z = 4). To verify such type of phase transition to the C2/c symmetry in $LuLiF_4$ compound the dependence of the enthalpy on pressure was calculated. The dependence demonstrates the growth of enthalpies of $I4_1/a$ and C2/c structure symmetries with the pressure. The enthalpy of structure with C2/c symmetry is higher than enthalpy of struc-

ture with symmetry $I4_1/a$ by 0.82 eV per elementary cell. It can be concluded that such type of phase transition is not carried out in $LuLiF_4$ compound. Also the enthalpy of P12/c1 structure symmetry has been calculated. It turned out to be higher than the enthalpy of structure with symmetry $I4_1/a$ by 0.76 eV per elementary cell. Thus $LuLiF_4$ structure with symmetry $I4_1/a$ is energetically most favorable.

4. Conclusion

Thus, in the present work the ferroelastic phase transition of $LuLiF_4$ scheelite ($I4_1/a$, Z = 4) structure under pressure was found at 10.5 GPa by means of DFT. The ferroelastic phase transition from the tetragonal structure to fergusonite one (C12/c1, Z = 4) was identified on the base of pressure dependence of the structural parameters, the order parameter and the cell volume. It was determined that this is the second order phase transition. The absence of phase transition to C2/c and to P12/c1 structure symmetries was shown.

Acknowledgements

This work was supported in part by the Ministry of Education and Science of Russian Federation.

References

References

[1] A. Grzechnik, K. Friese, V. Dmitriev, H.-V. Weber, J.-Y. Gesland, W. Crichton, Pressure-induced tricritical phase transition from the scheelite structure to the fergusonite structure in $LiLuF_4$, J. of Physics: Condensed Matter 17 (4) (2005) 763.

[2] P. Hohenberg, W. Kohn, Inhomogeneous electron gas 136 (1964) B864–B871.

[3] W. Kohn, L. J. Sham, Self-consistent equations including exchange and correlation effects, Phys. Rev. 140 (1965) A1133–A1138.

[4] G. Kresse, J. Furthmüller, Efficient iterative schemes for *ab initio* total-energy calculations using a plane-wave basis set, Phys. Rev. B 54 (1996) 11169–11186.

[5] P. E. Blöchl, Projector augmented-wave method, Phys. Rev. B 50 (1994) 17953–17979.

[6] J. P. Perdew, K. Burke, Y. Wang, Generalized gradient approximation for the exchange-correlation hole of a many-electron system, Phys. Rev. B 54 (1996) 16533–16539.

[7] S. L. Dudarev, G. A. Botton, S. Y. Savrasov, C. J. Humphreys, A. P. Sutton, Electron-energy-loss spectra and the structural stability of nickel oxide: an LSDA+U study, Phys. Rev. B 57 (1998) 1505–1509.

[8] A. Petrova, B. Minisini, O. Nedopekin, D. Tayurskii, Ab-initio investigations of $LuLiF_4$ compound under pressure, Journal of Physics: Conference Series 394 (1) (2012) 012021.

[9] L. Landau, The theory of phase transitions, Nature 138 (1936) 840–841.

[10] T. Tsunekawa, S.and Kamiyama, K. Sasaki, H. Asano, F. T., Precise structure analysis by neutron diffraction for $R\mathrm{NbO}_4$ and distortion of NbO_4 tetrahedra, Acta Crystallographica Section A 49 (1993) 595–600.

[11] F. Murnaghan, The compressibility of media under extreme pressures, Proceedings of the national academy of sciences of the United States of America 30 (9) (1944) 244.

[12] B. Minisini, L. E. Hadj, M. L. Fomena, N. V. Garderen, F. Tsobnang, A density functional study of the pressure induced phase transition in $LiYF_4$, Journal of Physics: Condensed Matter 18 (8) 2429.